

Our Ref: SW/BR

28 October 2020


Report 367501

Page 1 of 4

ONIRO Textiles
Fahrenheitbaan 4B
3439 MD Nieuwegein
Netherlands

Contact: Ninja Voorthuis

DATE RECEIVED	: 20 OCT 2020
FABRIC SUPPLIER	: Oniro Textiles
QUALITY/REFERENCE	: NIROXX LAMÉ
REPUTED FIBRE CONTENT	: 100% PES
FABRIC DESCRIPTION	: WOVEN
COLOUR/DESIGN	: 68025
BATCH NUMBER	: 419629 12118-1
ONIRO REF	: LAME
PERFORMANCE STANDARD	: GENERAL

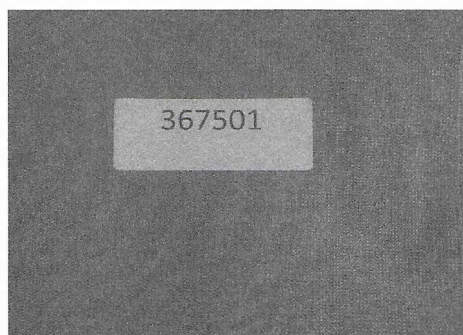

REQUEST: Colour fastness to wet & dry rubbing, light; tensile strength, tear strength, pilling, martindale abrasion & hydrostatic head

COMMENTS: Schildknecht flexing to follow on report 367501/2



S. WISEMAN
LABORATORY DIRECTOR



118 Lupton Avenue Leeds LS9 6ED
Tel:0044 (0) 113 248 8830 Fax:0044 (0) 113 248 0239 EMail: info@hstts.co.uk
Registered No. 2899980 VAT No. 613 4310 86

28 October 2020

Report 367501

Page 2 of 4

This report may not be reproduced except in full without the written approval of HSTTS. In all circumstances results of tests are implied as referring only to the sample supplied and should not be construed or interpreted on any other basis. The comments given in the report are for guidance only and are not a part of the results. Where specified in a test method, preconditioning in accordance with ISO 139 is not carried out as samples are exposed to the conditioning atmosphere specified within ISO 139 for a minimum of 16 hours prior to test.



118 Lupton Avenue Leeds LS9 6ED
Tel:0044 (0) 113 248 8830 Fax:0044 (0) 113 248 0239 EMail: info@hstts.co.uk
Registered No. 2899980 VAT No. 613 4310 86

28 October 2020

Report 367501

Page 3 of 4

COLOUR FASTNESS TO:

BS EN ISO 105-X12:2016 Rubbing

Colour	Test	Staining
	Dry, Face, Length	4-5
	Dry, Face, Width	4-5
	Wet, Face, Length	4-5
	Wet, Face, Width	4-5

BS EN ISO 105-B02:2014 Light Fastness Blue Wool 6

Shade change	
	6+

PHYSICAL

BS EN ISO 13934-1:2013 Tensile Strength 50mm Strip

	Length	Width
Mean	1897.3 N	1836.2 N

ISO 4674-1:2003 TONGUE TEAR STRENGTH

	Length	Width
Mean	138.0 N	175.4 N

BS EN ISO 12945-2:2000 PILLING MODIFIED MARTINDALE

Revs	Grade
500	4-5
1000	4-5
2000	4-5
5000	4-5

Sample tested: As received

Tested using standard worsted abradant as per BS EN ISO 12947-1



28 October 2020

Report 367501

Page 4 of 4

PHYSICAL

Abrasion Resistance BS EN ISO 12947-2: 1998 / BS EN 14465: 2003 Annex A §
12 kPa load.

Number of rubs to breakdown:
Head 1 100,000+
Head 2 100,000+
Head 3 100,000+
Head 4 100,000+

BS EN 20811:1992 (1996) Hydrostatic Head

Sample area 100cm²
Test atmosphere 20°C 65% R.H
Water temperature 20°C
Rate of rise of water pressure 60cm/min

Test 1	210 cms/H ₂ O
Test 2	229 cms/H ₂ O
Test 3	204 cms/H ₂ O
Test 4	227 cms/H ₂ O
Test 5	215 cms/H ₂ O
Mean	217 cms/H ₂ O

Tests indicated § are within the bounds of the flexible scope of accreditation operated by the laboratory.



118 Lupton Avenue Leeds LS9 6ED
Tel:0044 (0) 113 248 8830 Fax:0044 (0) 113 248 0239 EMail: info@hstts.co.uk
Registered No. 2899980 VAT No. 613 4310 86